

ISSN : 1386040096

ISSN : 1386040096


ISSN : 1386040096

Proceeding on the 2013 International Conference on

Advanced Technology to Support Sustainable Development

December 15th, 2013

**FAKULTAS
TEKNIK**



COMMITTEES

Steering Committee:

1. Dr. Fauzri Fahimuddin (FTUP)
2. Dr. A. Sarwiyana S. (FTUP)
3. Yarianto SBS, Ir. MSi (BATAN)
4. Irman Bustamam, Ir. M.Si (PT SI)
5. Prof. Dr. L. Serva (AF Consultant)
6. Dr. Antonio R. Godoy (AF Consultant)
7. Dr. Jan Kocourek (AF Consultant)

- Person in Charge for this Conference:


1. Ir. Eddy Djatmiko MT (FTUP)
2. Dra. Mari Indriana MSi (BATAN)

- Organizing Committee:

- Chairman : Prof. Drs. Syahbuddin MSc Ph.D (FTUP)
- Vice Chairman : M. Chairuddin ST MT (PTSI)
- Secretary : Dr. Ir. Dwi Rahmalina MT (FTUP)
- Catur Ria (FTUP)
- Financial treasurer : Sari Lavita SE (PT SI)
- Nurhayati SE (FTUP)
- MC : Niken Warastuti ST MT (FTUP)

Receptionist	: Dra. Nur Hidawati	(FTUP)
	Nugraheni S.H	(FTUP)
Seminar Section	: Ir. A.R. Indra Tjahjani MT	(FTUP)
	Ir. Muchtar Darmawan MT	(FTUP)
	Dra. Sri Rezeki C.N. M.Kom	(FTUP)
	Agus Aryanto	(BATAN)
	Adji Sunu Saderi	(PT SI)
Proceeding	: Ir. Siti Rohana N MT	(FTUP)
	L. Edhi Prasetya ST MT	(FTUP)
	Eko Prasetyo ST MT	(FTUP)
	Arief Tries Yuliyanto MT	(BATAN)
Furnishing and Documentation:		
	Ir. Hasan Hariri MT	(FTUP)
	Ir. Untung Priyanto MSi	(FTUP)
	Ir. Duta Widya Sasmojo	(FTUP)
	Suparmo	(FTUP)
Consumption	: Meity Purwantini	(BATAN)
	Titik Maryati S.Sos	(FTUP)
Editorial Board	: Prof. Dr. Ir. Djoko W. Karmiaji. MSc	(FTUP)
	Dr.Ir. Sudi Ariyanto	(FTUP)
	Dr. Ir. La Ode M. Firman MT	(FTUP)

ACKNOWLEDGEMENTS



AGENDA CONFERENCE

Time	Activity
08.30-09.30	Registry
09.30-09.45	Morning Coffee Break
09.45-09.50	Opening
09.50-10.00	Opening Speech by Rector of Pancasila University
10.00-12.00	<p>Session I, Panelis:</p> <ol style="list-style-type: none"> 1. Dr. Ir. Sukhyar: Chairman of the Geology Agency, Ministry of Energy and Mineral Resources, Indonesia, Title: Progress of Technology in Energy and Mineral Sector For Sustainable Development. 2. Prof. Dr. Leonello Serva: Member of the European Academy of Sciences and Arts – Class VI Environmental and Technological Sciences – Former Director of The Italian National Geology Survey, Italy). Title: Geological and Seismotectonic Aspects for the Site Evaluation of a Site for NPP Construction. 3. Dr. A.R. Godoy: Managing Director James J Johnson & Associates, Austria – Former Head of the IAEA's International Seismic Safety Centre, Austria. Title: Requirements For A Proper Siting Of A Nuclear Installation. 4. Dr. Jan Kocourek: AF Consult Switzerland Ltd., Director, Deputy Head of Nuclear Energy Business Unit, Switzerland. Title: Available Reactor Technologies Today and in the Future. <p>Moderator: Prof. Dr. Syahbuddin</p>
12.00-13.00	Lunch
13.00-15.00	<p>Session II, paper presentation in Mechanical, Industrial, Electrical, Informatics, Civil and Architecture Engineering Fields.</p> <p>Moderator: Prof. Dr. Binsar Hariandja, Dr. Jonbi, Dr. La Ode M. Firman, Ainil Syafitri ST. MT.</p>
15.00-15.15	Afternoon Coffee Break
15.15-17.00	<p>Session II (Continued), paper presentation in Mechanical, Industrial, Electrical, Informatics, Civil and Architecture Engineering Fields.</p> <p>Moderator: Prof. Dr. Binsar Hariandja, Dr. Jonbi, Dr. La Ode M. Firman, Ainil Syafitri ST. MT.</p>

CONTENTS

A. Mechanical Engineering & Industrial Engineering

R. HENGKI RAHMANTO, K.H. CHOI, AGUNG B, SUKMAJI I.C : Study Characteristics in Packed Tower of Liquid Desiccant Solar Cooling System Using Counter Flow Configuration	A-1
WIBISONO : Inspection Process Condensate Degasified Column on Urea Fertilizer Industry Using Gamma Ray	A-11
ATMA WINDRIJA : Body Design on Rural Transportation Vehicles With Safe and Save Energy Purpose	A-18
ADE NADJURI : Analysis of Electric Energy Savings in Electric Arc Furnace by Waste Heat Recovery System	A-27
SYAHBUDDIN A., MAINASSY : Friction Stir Welding for Butt Joint of Al Alloy 5083 ...	A-35
SETIADI : Structural Analysis of Motor Casing For Rocket RX-450h Using Stainless Steel 17-17PH	A-42
YOPI HANDOYO : Analysis on the Heat Exchanger Equipment on Economizer	A-49
TAUFIQUR ROKHMAN : Optimization of Geographical and Slope Solar Panel on Solar Radiation Intensity	A-56
MUCHTAR DARMAWAN, LOLA : Inventory Plan of 100 ml SS Bottle Raw Materials at JTS PT	A-72
YULITA VERANDA USMAN : A Model to Identify the Needed of Quality System Documents Using Risk Assessment Approach	A-84
EDDY DJATMIKO, AGRI SUWANDI : Tin Ball Casting Machine for Bangka Belitung Island	A-92
GINANDJAR, SETIYONO, ISMAIL : Improving the Quality of Metal Surface by Using Carbon and Nitrogen Diffusion Through Chemical Heat - Treatment in a Sealed Quench Furnace	A-102
HENDRI SUKMA, ISMAIL, RAMON TRISNO : Energy Analysis on the Smelting Process of Aluminum, Tin and Brass	A-109

DINO RIMANTHO, SITI ROHANA NASUTION : Effect of PM10 on Respiratory Problems of the Residents at Jalan MH. Thamrin Jakarta	A-118
RINI PRASETYANI, CHANDRA KURNIA PRIHANTONO : Maintenance Design of Injection Molding Machine by Using Reliability Centered Maintenance Method at Sodick Singapore PTE. LTD	A-129
LAELA CHAIRANI : Design of Maintenance Scheduling using Reliability Centered Maintenance Method	A-143
SETIYONO, I GEDE EKA LESMANA, RINI PRASETYANI : Comparison Analysis of Fuel Burn Reaction Using Air Oxidator and Oxygen Gas	A-150
WIBISONO : Diagnosing Pall Ring Configuration on Bulk Absorber Column at Urea Industry Using Nuclear Technique	A-159
SITI ROHANA NASUTION, BUDIADY : Fatigue Analysis Of Workers	A-167
RUDI HERMAWAN, EKO PRASETYO, AINIL SYAFITRI, YANI KURNIAWAN : Pengaruh Variasi Diameter Nozel dan Tinggi Permukaan Terhadap Daya yang Dihasilkan PLTMH.....	A-178
SORIMUDA HARAHAP, AHMAD ZAEKASYI : Analyzes The Performance of Centrifugal Pump In The Cooling System On-Line Welding	A-183

B. Electrical Engineering & Informatics Technology

FERRY HADARY, SYAIFURAHMAN, AYONG HIENDRO, NELLY WAHYUNI : A Comparison Between Pure Bixin and Kaolinite-Bixin Sensitized Solar Cells	B-1
A. SOFWAN, JAMALUDDIN : How To Increase The Power Quantity Of Solar Cell	B-7
WISNU BROTO, AINIL SYAFITRI : Analysis Up & Down - Conversion Concept Using Secondary Light Source As The Luminescence For Increasing Solar Cell Efficiency	B-16
UNTUNG PRIYANTO : Reduction Peak-to-Power Average Ratio using Clipping and Filtering Methods on OFDM System	B-25
AINIL SYAFITRI, WISNU BROTO : Pembangkit Sinyal Kendali Analog Untuk Pengendalian Motor Dengan Antarmuka PC Berbasis FPGA (MESA 5I20) dan Servo Amplifier (MESA 7I33)	B-34

SRI REZEKI CANDRA NURSANI, IMAN PARYUDI : Alternative Design Exploration using K-Nearest Neighbor Technique and Semantic Web Technology in an Energy Simulation Tool	B-42
SYAHRANY : Video Watermarking Using Discrete Cosine Transform and Fuzzy Logic Based on Human Visual System	B-48
YAASIINTA CARIENS, KARLINA KHIYARIN NISA : Simulation of Plant Growth Manipulation By Treating on its Genes Using C4.5 Rule Algorithm.....	B-59
FARID THALIB : Efficiency of Energy Consumption in Industrial Automation : Case Study Conveyor Belt Control System Using Integral Control Algorithm.....	B-68
IWAN SONJAYA, ADHI MAHENDRA : Daycare Information System Base on Web With Video Streaming	B-75
ANE PRASETYOWATI, NOOR SURYANINGSIH : Design and Simulation of Three-Layer Signaling System in Mobile Communication System at The Subscriber Receiver Using Microcontroller AT89S51	B-81
YAHYA SAMPURNA : Optimization of Lecture Schedule Using Tabu Search Algorithm	B-93
DUTA WIDYHA SASMOJO, WISNU BROTO : Pemetaan Daerah Potensi Banjir Dengan Segmentasi Data Digital Elevation Model Suti Kasus : Das Ciliwung di DKI Jakarta 2009..	B-115

C. Civil Engineering & Architecture

BINSAR HARIANDJA : Finite Element Analysis of Nonlinear Contact Problems with Mixed Eulerian-Lagrangian Description	C-1
IVINDRA PANE, JONBI : Advance in Chemical Admixture Technology and its Roles in Development of High Performance Concrete	C-17
PRAKTINO : Geopolymer Concrete With Superplasticizer	C-33
FAUZRI FAHIMUDDIN, ANIS R, PRAGANIF S, I KETUT SUCITA, RETNO P, VERA U : Load Distribution of Reinforcement Length in Concrete Using Grouting	C-43
DIPTYA ANGGITA : The Utilization of Natural Lighting For Energy Efficiency in Building.....	C-52
M. ALI BRAWI, HERAWATI ZETHA, ZULKARNAEN MOHAMMAD : Technology Selection in Airport Railway Project Using Value Engineering Approach.....	C-64

SURIPTO : Analysis of The Potential and Water Utilization of Cipancuh Reservoir in Indramayu Regency	C-73
PUTERA AGUNG M.A, FAUZRI FAHIMUDDIN : Effect of Berms on Sheet Pile Behavior (A Case Study of Depok Clay)	C-83
A. R. INDRA TIAHJANI : Modeling Selection Pavement of District Road	C-93

D. INVITED SPEAKERS

R. SUKHYAR: Progress of Technology in Energy and Mineral Sectors for Sustainable Development	D-1
SERVA, L. : Geological and Seismotectonic Aspects for the Site Evaluation of a Site for NPP Construction	D-28
Godoy, A.R.: Requirements For A Proper Siting Of A Nuclear Installation	D-68
Kocourek, J. : Available Reactor Technologies Today and in the Future	D-88

ADVANCES IN CHEMICAL ADMIXTURE TECHNOLOGY AND ITS ROLES IN DEVELOPMENT OF HIGH PERFORMANCE CONCRETE

Ivindra Pane¹ and Jonbi²

¹Laboratory of Structural Engineering

Bandung Institute of Technology, Bandung, Indonesia

²Department of Civil Engineering, Pancasila University

Jl. Srengseng Sawah, Lenteng Agung, Jakarta 12640, Indonesia

Abstract

Chemical admixture technology has significantly grown over the past 5 decades resulting in various products used by construction, ready mix and precast concrete industries. The advent of such technology is reviewed in herein and in particular, is related to usages and roles of admixture for developing high performance concrete. Concrete products such as self compacting concrete is found to benefit the most from advances in admixture technology. Guidelines for applying and specifying admixtures are also discussed at some length. In addition, applications describing usages of recently developed admixtures are also described in this paper.

Keywords: Chemical admixture, Concrete

1. INTRODUCTION

ACI 116R-00 [1] definition of admixture is a material other than water, aggregates, hydraulic cement, and fiber reinforcement, used as an ingredient of a cementitious mixture to modify its freshly mixed, setting, or hardened properties and that is added to the batch before or during the mixing (see also Fig. 1 for description).

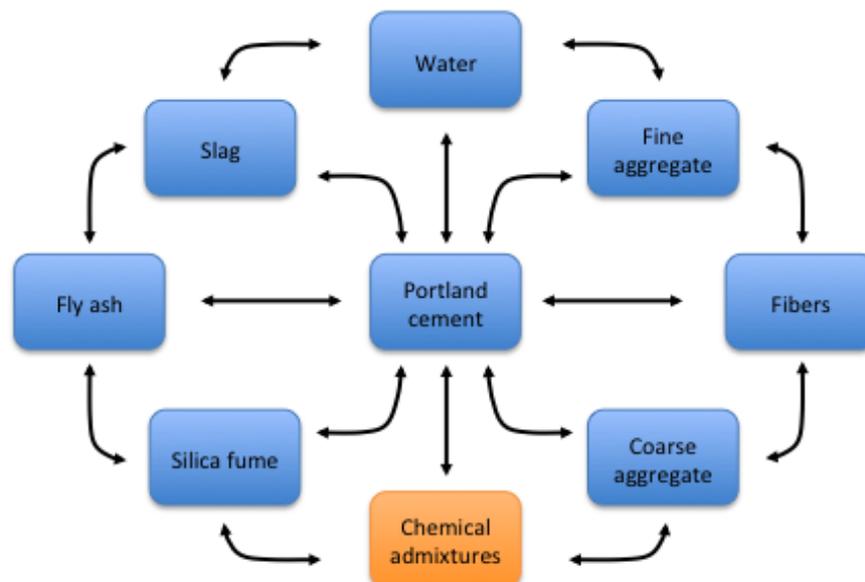


Figure 1. Schematic description of concrete ingredients and their interactions

Admixtures interact chemically with the ingredients of the concrete and affect its performance in the fresh and hardened state. They can exhibit special beneficial effects to concrete and enhance workability of the fresh mixture, and strength or durability of the hardened concrete.

Depending on the enhanced property, chemical admixtures can be classified as water reducers, superplasticizers, accelerators, retarders, air-entraining agents, corrosion inhibitors, alkali- aggregate expansion inhibitors, shrinkage reducing admixtures, etc.

a. Overview of Admixtures

Within the last 30 years admixtures have evolved significantly (see in Fig. 2), where the second millennium marks the development of next generations viscosity modifier and high range water reducer (HRWR) products.

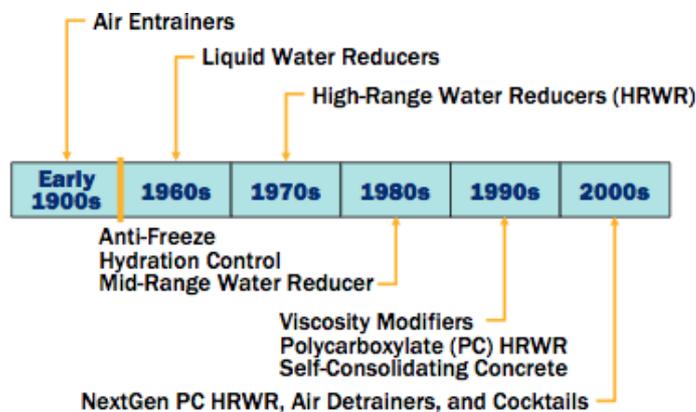


Figure 2. Evolution of chemical admixtures

Admixtures are classed according to function. There are five distinct classes of chemical admixtures [2]: air-entraining, water-reducing, retarding, accelerating, and plasticizers (superplasticizers). All other varieties of admixtures fall into the specialty category whose functions include corrosion inhibition, shrinkage reduction, alkali-silica reactivity reduction, workability enhancement, bonding, damp proofing, and coloring.

Water-reducing admixtures usually reduce the required water content for a concrete mixture by about 5 to 10 percent. Consequently, concrete containing a water-reducing admixture needs less water to reach a required slump than untreated concrete. The treated concrete can have a lower water-cement ratio. This usually indicates that a higher strength concrete can be produced without increasing the amount of cement. Recent advancements in admixture technology have led to the development of mid-range water reducers. These admixtures reduce water content by at least 8 percent and tend to be more stable over a wider range of temperatures. Mid-range water reducers provide more consistent setting times than standard water reducers.

Retarding admixtures, which slow the setting rate of concrete, are used to counteract the accelerating effect of hot weather on concrete setting. High temperatures often cause an increased rate of hardening which makes placing and finishing difficult. Retarders keep

concrete workable during placement and delay the initial set of concrete. Most retarders also function as water reducers and may entrain some air in concrete.

Accelerating admixtures increase the rate of early strength development, reduce the time required for proper curing and protection, and speed up the start of finishing operations. Accelerating admixtures are especially useful for modifying the properties of concrete in cold weather.

Superplasticizers, also known as plasticizers or high-range water reducers (HRWR), reduce water content by 12 to 30 percent and can be added to concrete with a low-to-normal slump and water-cement ratio to make high-slump flowing concrete. Flowing concrete is a highly fluid but workable concrete that can be placed with little or no vibration or compaction. The effect of superplasticizers lasts only 30 to 60 minutes, depending on the brand and dosage rate, and is followed by a rapid loss in workability. As a result of the slump loss, superplasticizers are usually added to concrete at the jobsite.

Corrosion-inhibiting admixtures fall into the specialty admixture category and are used to slow corrosion of reinforcing steel in concrete. Corrosion inhibitors can be used as a defensive strategy for concrete structures, such as marine facilities, highway bridges, and parking garages, that will be exposed to high concentrations of chloride. Other specialty admixtures include shrinkage-reducing admixtures and alkali-silica reactivity inhibitors. The shrinkage reducers are used to control drying shrinkage and minimize cracking, while ASR inhibitors control durability problems associated with alkali-silica reactivity.

b. High Performance Concrete

In a broader sense high performance concrete (HPC) can be considered as concrete in which certain characteristics are developed for a particular application and environments including: ease of placement, compaction without segregation, early-age strength, good long term mechanical and transport properties (compressive strength, elastic moduli, tensile strength, fracture toughness, permeability, durability), low risk of cracking, good dimensional stability [3].

Key features of HPC include usages of low water to binder ratio (w/b), optimal use of silica fume (and/or other mineral admixtures), smaller aggregates and fine sand, sufficient dosage of superplasticizers, occasional specialized treatments and application of pressure especially for ultra high strength concrete after mixing (at curing stage).

Performance measures and parameters that represent important aspects of HPC products can be studied by observing the macroscopic and microscopic behaviour including:

- i. Mechanical and physical properties (compressive and tensile strength, modulus of elasticity, fracture toughness, resistance to abrasion & wear, porosity, density)
- ii. Transport properties (permeability, sorptivity, chloride and sulphate penetration resistances)
- iii. Dimensional stability (thermal, shrinkage and creep)
- iv. Workability

Table 1. Microstructural parameters and their roles [3]

Microstructural Parameters	Role/effect	Macroscopic Behavior (NC)
Solid phase of hydrated paste (C-S-H gel)	Binder, load bearing	Strength, toughness, stiffness
Interface transition zone (ITZ)	Non uniform pores and hydration products	Strength, toughness
Capillary pores	Water filled space	Shrinkage, transport
Gel pores	Intrinsic pore in gel	Shrinkage, creep
Voids	Water filled space	Internal curing, shrinkage
Aggregate	Filler, load bearing	Strength, toughness, stiffness

Mechanical properties are responsible for high load bearing and mechanical resistance capabilities of RC or plain concrete members. Meanwhile, transport properties are tied closely to durability performance of concrete against penetrations of chloride and sulphate ions, leaching, etc. High stability against thermal, shrinkage and creep-induced deformations are desired for structural members to maintain their shapes and avoid additional stresses. In general, microstructure controls the macroscopic behavior of hardened concrete (points i, ii, and iii above). Therefore, observing HPC microstructure will lead to enhanced understanding on how characteristic behavior of HPC can be controlled. Workability is considered important as production and placement of well compacted and non-segregated fresh HPC require sufficient consistency and flow. Microstructural parameters and their roles are summarized in Table 1 above.

2. ADVANCES IN ADMIXTURE TECHNOLOGY

The effectiveness of an admixture depends upon factors such as type, brand, and amount of cementing materials; water content; aggregate shape, gradation, and proportions; mixing time; slump; and temperature of the concrete.

Admixtures being considered for use in concrete should meet applicable specifications as presented in Table 2 [2]. Trial mixtures should be made with the admixture and the job materials at temperatures and humidities anticipated on the job. In this way the compatibility of the admixture with other admixtures and job materials, as well as the effects of the admixture on the properties of the fresh and hardened concrete, can be observed. The amount of admixture recommended by the manufacturer or the optimum amount determined by laboratory tests should be used. Some types of admixtures will be discussed further in the following.

Table 2. Desired effects of various chemical admixtures and materials [2]

Type of admixture	Desired effect	Material
Accelerators (ASTM C 494 and AASHTO M 194, Type C)	Accelerate setting and early-strength development	Calcium chloride (ASTM D 98 and AASHTO M 144) Triethanolamine, sodium thiocyanate, calcium formate, calcium nitrite, calcium nitrate
Air detrainers	Decrease air content	Tributyl phosphate, dibutyl phthalate, octyl alcohol, water-insoluble esters of carbonic and boric acid, silicones
Air-entraining admixtures (ASTM C 260 and AASHTO M 154)	Improve durability in freeze-thaw, deicer, sulfate, and alkali-reactive environments Improve workability	Salts of wood resins (Vinsol resin), some synthetic detergents, salts of sulfonated lignin, salts of petroleum acids, salts of proteinaceous material, fatty and resinous acids and their salts, alkylbenzene sulfonates, salts of sulfonated hydrocarbons
Alkali-aggregate reactivity inhibitors	Reduce alkali-aggregate reactivity expansion	Barium salts, lithium nitrate, lithium carbonate, lithium hydroxide
Antiwashout admixtures	Cohesive concrete for underwater placements	Cellulose, acrylic polymer
Bonding admixtures	Increase bond strength	Polyvinyl chloride, polyvinyl acetate, acrylics, butadiene-styrene copolymers
Coloring admixtures (ASTM C 979)	Colored concrete	Modified carbon black, iron oxide, phthalocyanine, umber, chromium oxide, titanium oxide, cobalt blue
Corrosion inhibitors	Reduce steel corrosion activity in a chloride-laden environment	Calcium nitrite, sodium nitrite, sodium benzoate, certain phosphates or fluosilicates, fluocaluminates, ester amines
Dampproofing admixtures	Retard moisture penetration into dry concrete	Soaps of calcium or ammonium stearate or oleate Butyl stearate Petroleum products
Foaming agents	Produce lightweight, foamed concrete with low density	Cationic and anionic surfactants Hydrolyzed protein
Fungicides, germicides, and insecticides	Inhibit or control bacterial and fungal growth	Polyhalogenated phenols Dieldrin emulsions Copper compounds
Gas formers	Cause expansion before setting	Aluminum powder
Grouting admixtures	Adjust grout properties for specific applications	See Air-entraining admixtures, Accelerators, Retarders, and Water reducers
Hydration control admixtures	Suspend and reactivate cement hydration with stabilizer and activator	Carboxylic acids Phosphorus-containing organic acid salts
Permeability reducers	Decrease permeability	Latex Calcium stearate
Pumping aids	Improve pumpability	Organic and synthetic polymers Organic flocculents Organic emulsions of paraffin, coal tar, asphalt, acrylics Bentonite and pyrogenic silicas Hydrated lime (ASTM C 141)
Retarders (ASTM C 494 and AASHTO M 194, Type B)	Retard setting time	Lignin Borax Sugars Tartaric acid and salts
Shrinkage reducers	Reduce drying shrinkage	Polyoxyalkylene alkyl ether Propylene glycol
Superplasticizers* (ASTM C 1017, Type 1)	Increase flowability of concrete Reduce water-cement ratio	Sulfonated melamine formaldehyde condensates Sulfonated naphthalene formaldehyde condensates Lignosulfonates Polycarboxylates

Type of admixture	Desired effect	Material
Superplasticizer* and retarder (ASTM C 1017, Type 2)	Increase flowability with retarded set Reduce water-cement ratio	See superplasticizers and also water reducers
Water reducer (ASTM C 494 and AASHTO M 194, Type A)	Reduce water content at least 5%	Lignosulfonates Hydroxylated carboxylic acids Carbohydrates (Also tend to retard set so accelerator is often added)
Water reducer and accelerator (ASTM C 494 and AASHTO M 194, Type E)	Reduce water content (minimum 5%) and accelerate set	See water reducer, Type A (accelerator is added)
Water reducer and retarder (ASTM C 494 and AASHTO M 194, Type D)	Reduce water content (minimum 5%) and retard set	See water reducer, Type A (retarder is added)
Water reducer—high range (ASTM C 494 and AASHTO M 194, Type F)	Reduce water content (minimum 12%)	See superplasticizers
Water reducer—high range—and retarder (ASTM C 494 and AASHTO M 194, Type G)	Reduce water content (minimum 12%) and retard set	See superplasticizers and also water reducers
Water reducer—mid range	Reduce water content (between 6 and 12%) without retarding	Lignosulfonates Polycarboxylates

* Superplasticizers are also referred to as high-range water reducers or plasticizers. These admixtures often meet both ASTM C 494 (AASHTO M 194) and ASTM C 1017 specifications.

a. Superplasticizer

Superplasticizers cause dispersion into smaller cement particles of coarse agglomerates which predominate in the cement paste of the concrete mix [4]. Due to the dispersion effect, there is a fluidity increase in the cement mixture. In the past time the dispersion effect was ascribed only to the development of the same electrostatic (negative) charge on the cement particles [5]. The electrostatic attractive forces, existing among cement particles and causing agglomeration, would be neutralized by the adsorption of anionic polymers negatively charged, such as SNF or SMF, for the presence of SO_3^- groups on the surface of cement particles. The dispersion of cement particles would be related with the electrical repulsion produced by the negatively charged groups (SO_3^-) on the other side of the main polymer chain (Fig. 3).

Four major groups of superplasticizers are:

- i. Sulfonated naphthalene-formaldehyde condensate (SNF)
- ii. Sulfonated melamine-formaldehyde condensate (SMF)
- iii. Modified lignosulfonate (MLS)
- iv. Polycarboxylates

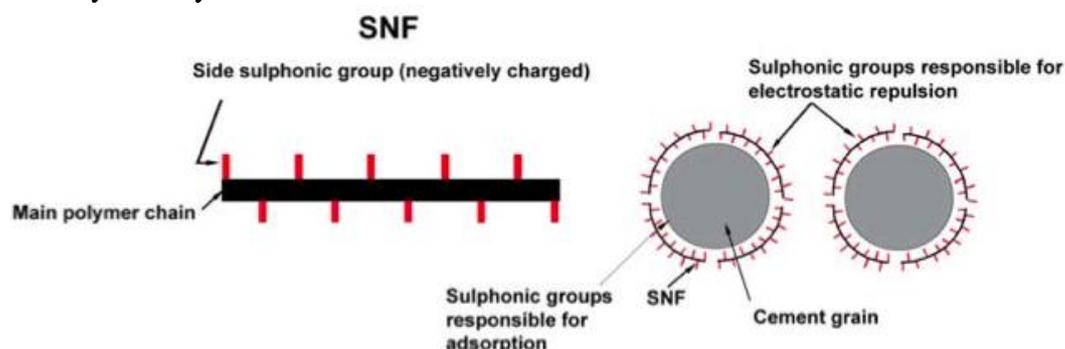


Figure 3. Schematic picture of sulfonated polymer (SNF) and its electrostatic repulsion effect on the dispersion of cement particles

Hamada et al. [6] developed a new family of acrylic polymers based on the following changes with respect to the PC-based superplasticizer:

- i. A polyether (PE) based superplasticizer with much longer side chains of ethylene oxide (EO): 130 moles of EO instead of 10-25 moles as in traditional PC-based superplasticizer (Fig. 4); this change produces a lower adsorption speed and reduces the typical retarding effect related to the early adsorption;
- ii. A modified PE-based superplasticizer where a great number of carboxylic groups are replaced by a slump- loss controlling agent (SLCA) to achieve a still higher slump retention with minimal setting retardation: indeed, due to the relatively low number of carboxylic groups in SLCA (Fig. 4) the initial adsorption and the dispersing effect are negligible as well as the setting retardation; however, subsequently to the hydrolytic effect related with the OH^- presence in the aqueous phase of the cement paste, the number of carboxylic units increases (Fig. 4) and the slump can still increase by prolonging the mixing time due to the increasing adsorption of the polymer on the surface of the cement particles.

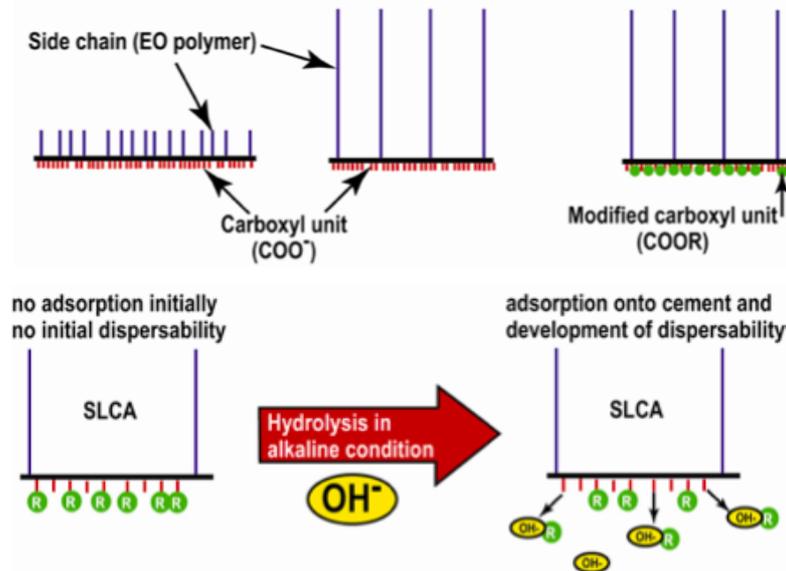


Figure 4. The schematic molecular structure of polycarboxylate type (PC), polyether type and slump-loss- controlling agent superplasticizer (SLCA) [4]

b. Viscosity Modifying Admixtures

Viscosity modifying admixtures (VMA) is a material added to concrete that changes its viscosity and improves the stability of the mixture [7]. Types of VMA include:

- i. Cellulose
- ii. PEG
- iii. Glycol derivative Natural Gums (Welan, Diutan, Guar)

The key function of VMA is to modify the rheological properties of the cement paste. The rheology of fresh concrete can be mainly described by its yield point and plastic viscosity (see also Fig. 5):

- i. The yield point describes the force needed to start the concrete moving. Yield point is related to the workability of the concrete and may be assessed by tests such as the slump value (EN 12350-2).
- ii. Plastic Viscosity describes the resistance of a concrete to flow under external

stress. Viscosity is caused by internal friction. The speed of flow of concrete is related to its plastic viscosity as shown in the diagram below and may be assessed by the T_{500} time during a slump flow test (prEN 12350-8) or by the time to flow through a V Funnel (prEN 12350-9).

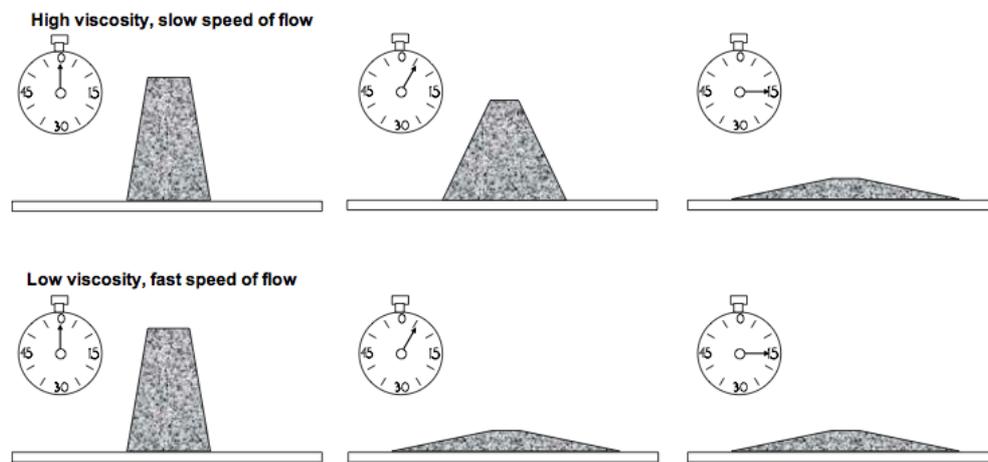


Figure 5. Illustration of effect of VMA [7]

The balance between the yield point and the plastic viscosity is key to obtaining the appropriate concrete rheology. VMA's change the rheological properties of concrete by increasing the plastic viscosity but usually cause only a small increase in the yield point. Admixtures which decrease the yield point are called plasticizers and are often used in conjunction with a VMA to optimize the yield point. VMA also provides cushion to aggregate particles, adds more "body" or "cream" to concrete, keeps particles/aggregates suspended, and reduces segregation, as illustrated by the following figure.



Figure 6. Example illustrating effect of VMA

c. Rheology Controlling Admixtures

Rheology: the study of the deformation and flow of matter under the influence of an applied stress, which might be shear stress or extensional stress. A rheology controlling admixture shall be used to facilitate the extrusion and consolidation of low-slump concrete (< 75 mm) and placement and consolidation of normal slump concrete (≥ 75 mm). The rheology-controlling admixture may also be used in mortar and grout applications if desired. The admixture effects include:

- i. Lowers force required to initiate flow, without affecting the viscosity
- ii. Improves response to vibration

- iii. Lubrication effect
- iv. Enhances consolidation

The rheology-controlling admixture shall not adversely affect the setting characteristics, air content or hardened properties of the concrete, mortar or grout mixture. Use of the rheology-controlling admixture shall exhibit the following properties or provide the following benefits compared to untreated concrete of similar mixture proportions:

- i. Improve the workability or flow of bulk concrete, and improve the response to vibration without a significant change in slump. Low-slump concrete containing the rheology-controlling admixture shall show a minimum increase in relative volume flow of 30%, as measured by the Test Method for Volume Flow.
- ii. Lower the yield stress, or force required to initiate flow, of the bulk concrete mixture, without necessarily changing its viscosity.
- iii. Not disperse cement, but impart a lubricating effect to concrete that influences particle to particle interactions, thereby facilitating flow of the bulk concrete mixture during consolidation.
- iv. Concrete properties shall be within tolerances specified in ACI 117.

d. Shrinkage-reducing admixtures

Shrinkage-reducing admixtures, introduced in the 1980s, have potential uses in bridge decks, critical floor slabs, and buildings where cracks and curling must be minimized for durability or aesthetic reasons. Propylene glycol and polyoxyalkylene alkyl ether have been used as shrinkage reducers. Drying shrinkage reductions of between 25% and 50% have been demonstrated in laboratory tests. These admixtures have negligible effects on slump and air loss, but can delay setting. They are generally compatible with other admixtures.

e. Hydration Controlling Admixtures

Hydration controlling admixtures became available in the late 1980s. They consist of a two-part chemical system: (1) a stabilizer or retarder that essentially stops the hydration of cementing materials, and (2) an activator that reestablishes normal hydration and setting when added to the stabilized concrete. The stabilizer can suspend hydration for 72 hours and the activator is added to the mixture just before the concrete is used. These admixtures make it possible to reuse concrete returned in a ready-mix truck by suspending setting overnight. The admixture is also useful in maintaining concrete in a stabilized non-hardened state during long hauls. The concrete is reactivated when it arrives at the project. This admixture presently does not have a standard specification.

3. ROLES OF ADMIXTURE IN DEVELOPMENT OF HPC

a. Role of Superplasticizer

We will begin this chapter by discussing the role of superplasticizers. The reasons that superplasticizers are much more important than any other chemical admixture is the number of improvements which can be achieved by its use. Fig. 7 summarizes these schematically [4].

When a superplasticizer is used as a water reducer at a given workability (I in Fig. 7), it improves the properties of hardened concrete and, in particular, increases strength and durability due to the reduction in capillary porosity and permeability, both related to a lower water-cement ratio (w/c).

Another mode of use of superplasticizers involves reduction of both water and cement, so that workability and strength of the concrete with superplasticizer are the same as those of the control concrete without admixture (II in Fig. 7). Since superplasticizers in this case act as cement reducers, they are capable of reducing the heat of hydration, a property that is useful for concreting in hot climates or massive structures. There is also a beneficial effect on the reduction in shrinkage and creep due to the higher aggregate/cement ratio related to the reduction in cement content and the increase of aggregate compensating the volume decrease of cement and water.

Finally, if superplasticizers are added without modifying water and cement content, concrete workability improves (III in Fig. 7). This is perhaps the most useful effect of superplasticizers for placing concrete in areas of high steel content that require a more workable mixture.

The changes (I) and (II) in the presence of superplasticizers can be carried out without admixture by increasing the cement-content (IV) or both cement and water at a given w/c (V) respectively. Both changes (IV) and (V) occur with higher shrinkage, creep and heat of hydration for the increase of the cement content.

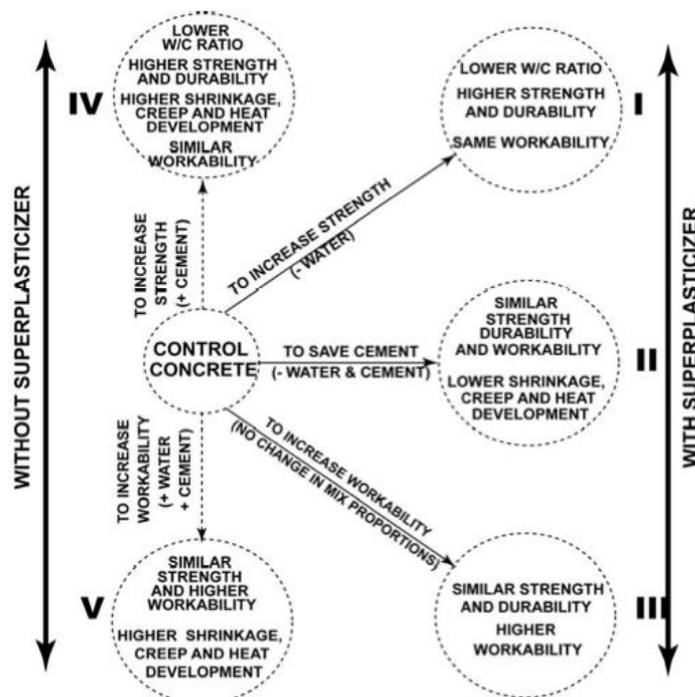


Figure 7. Roles of superplasticizers

b. Guidelines to Usage of Admixtures for HPC

The following guidelines are derived based on requirements provided by British Standard (BS) [8]. Except in special cases such as high-strength concrete, the maximum dosage of concrete admixtures is limited, by 5.2.6 of BS EN 206-1, to 50 g/kg cement. For low dosages of less than 2 g/kg cement, the admixture has to be dispersed in part of the mixing water.

The performance of concrete admixtures is controlled in BS EN 934-2 by requirements related to the main function for single-function admixtures and to the main function and secondary functions for dual- or multi-function admixtures. These performance requirements are shown in Table 2.

In addition there are general performance requirements applying to all admixtures; these include:

- i. Effect on setting time;
- ii. Effect on compressive strength;
- iii. Effect on air content in fresh concrete;
- iv. Water soluble chloride content;
- v. Alkali content as $\text{Na}_2\text{O}_{\text{eq}}$.

The performance of admixtures is determined by using reference concrete. The test mix (with admixture) is compared with the control mix (without admixture). The chloride and alkali contents also have to be measured and declared. Test procedures for admixtures are given in the BS EN 480 series, Admixtures for concrete, mortar and grout – Test methods. The chloride content of all concrete is limited by Table 10 of BS EN 206–1 and the contribution of admixtures to the chloride content can be calculated. BS EN 934–2 limits admixture chloride content to a maximum of 0.10% or the manufacturer’s stated value. Where the alkali content is limited in accordance with 5.2.2.2 of BS 8500–2, the contribution from admixtures can be calculated. BS EN 934–2 requires the manufacturer to state the maximum alkali content of each admixture.

Tabel 2. Performance requirement for admixtures

Type of admixture	Performance requirement	Value in BS EN 934–2
Water reducing/plasticizing	Water reduction at equal consistence	Reduction \geq 5%
High-range water reducing/superplasticizing	Water reduction at equal consistence	Reduction \geq 12%
	Increase in consistence at equal w/c ratio	Slump increase \geq 120 mm
Water retaining	Reduction in bleeding	Reduction \geq 50%
Water resisting	Reduction in capillary absorption	Reduction \geq 50% by mass
Air entraining	Air void characteristics in hardened concrete	Spacing factor \leq 0.200 μm
Set accelerating	Reduction in initial setting time	Reduction \geq 40% at 5°C
Hardening accelerating	Compressive strength at 1 day	Increase \geq 20% at 20°C
	Compressive strength at 2 days	Increase \geq 30% at 5°C
Set retarding	Increase in initial and final setting times	Initial increase \geq 90 min. Final increase \leq 360 min.
Set retarding/water reducing/plasticizing	Water reduction at equal consistence	Reduction \geq 5%
	Increase in initial and final setting times	Initial increase \geq 90 min. Final increase \leq 360 min.
Set retarding/high-range water reducing/super plasticizing	Water reduction at equal consistence	Reduction \geq 12%
	Increase in consistence at equal w/c ratio	Slump increase \geq 120 mm
	Increase in initial and final setting times at equal consistence	Initial increase \geq 90 min. Final increase \leq 360 min.
Set accelerating/water reducing/plasticizing	Water reduction at equal consistence	Reduction \geq 5%
	Reduction in initial setting time	Reduction \geq 30 min. at 20°C and \geq 40% at 5°C

c. Specifying Admixtures

Admixtures will normally be used in designed and designated concrete. The concrete producer should be left to select the most appropriate admixture to contribute to achieving the specified concrete properties. For ready-mixed concrete, the type of admixture used is stated on the delivery ticket.

There is no reason to prohibit the use of admixtures. For designed concrete, admixtures are frequently used to help achieve the following properties:

- i. Compressive strength;
- ii. consistence;
- iii. Density;
- iv. Air content;
- v. Strength development;
- vi. Retarded stiffening;
- vii. Resistance to water penetration;
- viii. Other special properties (e.g. accelerated stiffening, high early strength development).

Clause 3.1.3 of BS EN 934–2 advises that “trial tests should be carried out with the materials to be used on site to find the dosage necessary to achieve the desired result”. The concrete producer may well have the results of such tests, which should be obtained before specifying the type and dose of admixture for a specific concrete mix.

The specifier should take into account the following:

- i. Admixtures of the same type from different manufacturers may well require different doses to achieve the desired effect;
- ii. The effect of admixtures is dependent on the particular cement, additions and aggregates used in the concrete.

The specified dose should be within the recommended range of dosage for the particular type and brand of admixture. This information is provided by the manufacturer.

When a combination of admixtures is used it is important to obtain data for the performance of mixes incorporating the particular combination of admixtures.

4. APPLICATIONS

a. Self compacting HPC

Self-compacting concrete is a concrete that is able to flow and consolidate under its own weight, completely fill the formwork even in the presence of dense reinforcement, whilst maintaining homogeneity and without the need for any additional compaction.

Self-compacting concrete may be classified in three types: the powder type, viscosity agent type and the combination type,

- i. The powder type SCC is characterised by the large amounts of powder (all material < 0.15 mm) which is usually in the range of 550 to 650 kg/m³. This provides the plastic viscosity and hence the segregation resistance. The yield point is determined by the addition of superplasticizer.
- ii. In the viscosity type SCC the powder content is lower (350 to 450 kg/m³). The segregation resistance is mainly controlled by a VMA and the yield point by the addition of superplasticizer.
- iii. In the combination type of SCC the powder content is between 450 to 550 kg/m³ but in addition the rheology is also controlled by a VMA as well as an appropriate dosage of the superplasticizer.

In a well proportioned SCC the major variation in the composition during production at the plant comes from normal changes in the moisture content of the sand and the coarse aggregates. Variations of 1.5 % moisture content are typical for aggregate will lead to a change of 10 to 15 liters/m³ of free water in the concrete mix. This will lead to significant variations in the flow and cohesion properties of the concrete being observed from one batch to another on the same day or from one day to another.

Viscosity Modifying Admixtures make the concrete more tolerant to variations in the water content of the mix so that plastic viscosity is maintained and segregation prevented. The concrete has become more robust to small but normal changes in the moisture of the aggregate. VMA's are a family of admixtures designed for specific applications [7]. They are used to:

- i. Reduce segregation in highly flowable/self compacting concrete
- ii. Reduce washout in underwater concrete
- iii. Reduce friction and pressure in pumped concrete
- iv. Compensating for poor aggregate grading, especially a lack of fines in the sand
- v. Reducing powder content in self compacting concrete
- vi. Reduce bleeding in concrete
- vii. Improve green strength in semi-dry concrete

Viscosity Modifying Admixtures are not a substitute for poor quality constituents or mix design. Aggregates with a good grading curve should always be used for SCC and for high workability concrete as a lack of fines in aggregates will affect the rheology and may contribute to segregation and settlement. However, where suitable aggregates are not economically available the required rheology of the mix can often be achieved by utilizing a VMA to provide a more homogenous and cohesive concrete.

Potential benefits of a VMA in SCC may be summarized as follows:

- i. Less sensitive to variations in the moisture content of the aggregate
- ii. The effects of small changes in the materials properties are minimized
- iii. Lower powder content
- iv. Reduces the level of production control
- v. Allows more fluid mixes to be used without the risk of segregation
- vi. Improving placing rate
- vii. Reduced risk of segregation and bleeding
- viii. Reduced formwork pressure by thixotropic effect
- ix. Better surface appearance

An overdose of VMA could make the fresh concrete mix too cohesive and slow the placing rate. This effect can usually be overcome by increasing the superplasticizer content.

b. Benefits of Combining Admixtures

One can combine water reducer and HRWR and expect the following:

- i. Low water content of concrete, i.e. zero slump (initial water content is critical)
- ii. Add Type A (2.0 oz/cwt) to increase to 2 in slump
- iii. Add type F (9.0 oz/cwt) to increase to 11 in slump
- iv. Higher strengths, lower shrinkage High slump retention
- v. Good pumpability

Combination of mid-range water reducer and retarder can be expected to:

- i. High temperatures, low humidity
- ii. Longer working time
- iii. Better control over set time
- iv. Typically 8.0 oz/cwt and 2.0 oz/cwt, respectively

Another effect is the combination of hydration stabilization admixture (HAS) and accelerator and HRWR, which can be expected to provide:

- i. Job Constraints/Specifications,
 - 3000 psi in 6 hrs, Type I/II cement
 - 2 yd³ bucket placement, 8 yd³ per truck
 - 45 min haul to job
 - No staging of trucks, tight jobsite
- ii. Admixture Sequencing:
 - Type F added to truck
 - Type C added after Type F
 - Type B added after Type F and C

5. CONCLUDING REMARKS

The following study has collected and gathered information on recent advances of admixture technology and present applications where high performance concrete can benefit from admixture usage. Desired effects of admixtures and their relations to performance requirement have also been presented.

Important application examples include usage of advanced types of admixtures such as viscosity modifying admixture (VMA), whether alone or as well as together with superplasticizer, for self compacting concrete (SCC). In addition, an example on combined use of two or more types of admixture to achieve some desired effects has also been provided.

In summary, admixture technology can contribute significantly to development of high performance concrete. Recent applications have also shown more advanced potentials for effective use of more than one admixtures together and for reducing consumption of cement and therefore, leading to practices of sustainable construction.

REFERENCES

- [1]. ACI 116R-00 Cement and Concrete Terminology
- [2]. Kosmatka, S.H., Kerkhoff, B., Panarese, W.C. Design and Control of Concrete Mixtures, 14th Edition.
- [3]. Pane, I., Jonbi, High Performance In Situ Concrete: Choosing Suitable Materials and Methods, 6th Civil Engineering Conference in Asian Region (CECAR 6) and HAKI annual Conference, Jakarta, Indonesia, 2013
- [4]. Collepardi, M., Admixtures-enhancing concrete performance, Engineering Concrete, Ponzano Veneto (Italy) 6th International Congress, Global Construction, Ultimate Concrete Opportunities, Dundee, U.K. – 5-7 July 2005
- [5]. Compater C., Nonat A., Pourchet S., Mosquet M., and Maitresse P., The Molecular Parameters and the Effect of Comb-Type Superplasticizers on Self-Compacting Concrete: A Comparison of Comb-Type Superplasticizer Adsorption onto a Basic Calcium Carbonate Medium in the Presence of Sodium Sulphate, Proc. 7th

- CANMET/ACI Int. Conf. Superplasticizers and Other Chemical Admixtures In Concrete, ACI SP 217, Berlin, Germany, 20-24 October, pp. 195-210 (2003).
- [6]. Hamada D., Sato H., Yamamuro H., Izumi T., and Mizunuma T., Development of Slump-Loss Controlling Agent with Minimal Setting Retardation, Proc. 7th CANMET/ACI Int. Conf. Superplasticizers and Other Chemical Admixtures In Concrete, ACI SP 217, Berlin, Germany, 20-24 October, pp. 127-142 (2003).
- [7]. Guidelines for Viscosity Modifying Admixtures For Concrete, European Federation of Concrete Admixture Associations (www.efca.info), 2006
- [8]. Specifying constituent materials for concrete to BS EN 206–1/BS 8500.

Question:

Answer: