# Thermal Enhancement for Paraffinic Thermal Energy Storage by Adding Volcanic Ash

by Ismail Ismail

**Submission date:** 17-Jun-2021 05:53AM (UTC+0700)

**Submission ID:** 1607699480

**File name:** canic\_Ash\_VANOS\_Journal\_of\_Mechanical\_Engineering\_Education.pdf (350.22K)

Word count: 5090 Character count: 27273





## **IOURNAL OF MECHANICAL ENGINEERING EDUCATION**

https://jurnal.untirta.ac.id/index.php/vanos ISSN 2528-2611, e-ISSN 2528-2700 Volume 6, Number 1, May 2021, Pages 77-88



# Thermal Enhancement for Paraffinic Thermal Energy Storage by Adding Volcanic Ash

Dwi Chandra Adhitya<sup>1</sup>, Dwi Rahmalina<sup>1</sup>, Ismail<sup>1</sup>, Muhammad Nurtanto<sup>2</sup>, Hamid Abdillah<sup>2</sup>

<sup>1</sup>Department of Mechanical Engineering, Pancasila University Raya Lenteng Agung Street No.56-80, RT.1/RW.3, Srengseng Sawah, Jakarta, Kota Jakarta Selatan, Daerah Khusus Ibukota Jakarta 12640

<sup>2</sup>Department of Mess anical Engineering Education, University of Sultan Ageng Tirtayasa Ciwaru Raya Street, No. 25, Serang, Banten, 42117

Corresponding author: Dwichandra\_a@yahoo.com

Accepted: 24 March 2021. Approved: 5 May 2021. Published: 23 April 2021

### ABSTRACT

Thermal energy storage has a good opportunity to be applied in engineering field, especially for low temperature application like automotive thermal management system. Paraffinic is a better option and considered as a good phase change material with main advantages like economically feasible, non-corrosive and safe. The main drawbacks of paraffinic system are low thermal conductivity and supercooling effect. The effort to improve the performance for paraffinic system is by g sensible material. Considering the spread of volcano in Indonesia, it can be used as sensible material for paraffinic system. The aim of the research is to examine the volcanic ash characteristic and the effect of sand addition on the paraffinic system. a standardized approach for sand examination is done and the effect of the hybrid PCM (90% paraffin and 10% volcanic ash mass ratio) are studied. The overall performance of hybrid PCM is better than pure paraffin where the vapor point of hybrid PCM is increased and there is no supercooling phenomenon observed.

**Keywords:** Automotive thermal management system, Paraffin, PCM, Thermal energy storage, Volcanic ash

### INTRODUCTION

The thermal energy storage system is an essential key in utilizing heat energy sources, such as Concentrated Solar Power (CSP) systems [1][2][3]. Thermal energy storage systems can also be developed for solar water heating systems [4][5][6][7], seawater desalination systems [8][9][10], and also the utilization of thermal waste in vehicles through vehicle thermal management systems [11][12][13]. Heat storage systems can also be utilized for domestic warm water supply systems for sub-tropical countries [14].

Focused at the application of the Concentrated Solar Power (CSP), the thermal energy storage plays the critical role to improve the overall performance and reducing energy cost because with proper thermal energy storage the system can work at a longer period (during the night time or cloudy day) [15][16][17]. The application of thermal storage in a CSP system can be addressed according to the working temperature of the CSP system [18][19][20]. There are three types of thermal energy storage material based on the characteristic of the material; there are sensible, latent and thermochemical heat [21]. Thermochemical heat has the highest theoretically capacity but has not widely used for real application and still under research and development phase [22]. Sensible heat has mature technology and widely used in various application, especially for water heater storage, but it has a drawback that it depends on the volume and mass of the storage material. Thus it has lower energy density which increased the cost per unit energy [23][24]. An alternative option that can be further developed is the phase change material (PCM) latent heat storage system [25].

The recommended PCM material is generally paraffin-based. Paraffin is a material that is very commonly used as a PCM material with consideration of safer, stable, non-corrosive and low prices and a reasonably wide temperature range (5-80°C) [26][27][28]. One of the main challenges of applying paraffin as PCM is low thermal conductivity and low enthalpy of phase change. An alternative solution to improve the nature of paraffin as a TES is through integration with sensible heat materials, such as water, sand and rocks. The application of sand is recommended because it has good thermal conductivity, abundant availability and considered cheap [29].

There were some researched to improve the performance of PCM based paraffin for thermal storage application. The effort mostly by g sensible material or additive and also enhancement the packaging model of the material. [30] developed PCM material based high-density polyethene (HDPE) composites with expanded graphite (EG) and ammonium polyphosphate (APP) found that the additional help to increase the temperature of the maximum weight loss of the PCM composites at 650°C. S. [31] simulated dynamic charging characteristics with spherical capsules using paraffin as a heat storage material for solar heat storage system the influence of porosity of packed bed on time for complete solidification is not so significant. [32] analyzed the addition of aluminum foil from waste material to increase the thermal conductivity of the paraffin storage material using paraffin wax with 8% w/w of aluminum foils and found the thermal conductivity increased up to 0.63 W/mK. [24] a suitable proportion of expanded graphite (EG) into the paraffin can enhance the heat transfer rate, thus improve the thermal efficiency of the whole heat storage system.

[33] proved that the addition of TiO2-Ag nanocomposite particles able to improved thermal properties of PCM storage. [34] studied the effect of nanoencapsulation of paraffin wax with a polyurethane-based shell and found the energy storage efficiency and the energy storage capacity of adequate nanocapsules are 80.2% and 97.5%, respectively. [35] investigated combination of paraffin and carbon-coated nanoscroll to improve the conductivities and found that the thermal conductivities of the paraffin and carboncoated nanoscroll were increased by 1.98, 1.92, 2.7 and 2.01 times compared to pure paraffin.

The addition of additive material can be considered as an easy and cheap method to improve paraffin performance as thermal energy storage. For lower temperature application, the addition of sensible heat material like water, rock and sand considered

as the easiest and cheapest way to enhancing the paraffin performance [36][37][32]. The recommended working area for sensible-PCM as thermal storage in the solid-liquid transition is known better than the liquidvapor phase and the solid-solid phase [38] [39][40][41]. [42] conducted an experimental test for hybrid sensible/latent storage for hot water applications by utilizing commercial paraffin grade and hydrate salt mixture and found that the heat storage capacity increased for the system. For combined system (hybrid material). [43] states that combined sensible-latent material can be used to tackle the drawback of PCM material. However, in most cases, it leads to another problem, such as higher cost and material compatibilities issues. Therefore, the addition of sensible material must take account of these barriers.

The addition of sensible material should be done carefully because it will decrease the total amount of the paraffin incorporated in the PCM and thus, the overall thermal efficiency and capacity will be reduced. From the data references and previous researches, the maximum of the additive in the PCM should be equal or lower than 50% [44]. Sand is well known sensible thermal storage material. The application of sand is recommended because it has good thermal conductivity, abundant availability and low cost [45][46][47][43]. It is crucial to examine the detail properties and its effect of the PCM performance obtain better understanding to specify the proper

application of the thermal storage and also the fabrication of the bed storage [48].

The data from previous research is limited and do not specify the type of sand, sand properties, both chemical elements and grain size and the proportion between sand and the paraffin. To study the effect of the sand for the PCM, it needs to be further investigated the chemical and physical properties from the sand. In this study, the sand comes from volcanic ash. The primary motivation to choose volcanic sand as the sensible material is due to the higher metal content of this sand. The next consideration is that the bulk size of the sand is generally finer than other sand so that it is expected to get an average size that is larger than the bulk size without having to be further processed to reduce the size of the sand grains. Besides, the potential of volcanic ash in Indonesia is quite vast due to volcanoes, so it is easily obtained. The study aims to examine the chemical and physical properties of the sand. Once the data from the sand has obtained, experimental testing is done by mixing paraffin with sand in different portions and grain size. From the experimental result the detailed phase-change transition of the paraffin, the temperature of the phase transition and the duration for charging and discharging the sample can be investigated; thus, a detailed conclusion of the material performance can be made, and it can be used as reliable references for the further application of the material as thermal storage.

### RESEARCH METHOD

The sand from volcanic ash for this research does not have MSDS so the first step that needs to be studied is to evaluate the chemical content of the sand and its intensive properties. The preparation is started by ensure the particle size uniformity of the sand through the sieve test. The sieve test was carried out to determine the average size of the sand particles with the target particle size used is 44  $\mu$ m. The sieve test procedure follows the NIST 906-1 standard [48].

Furthermore, chemical content in the uniformed sand was observed using an atomic absorption spectrometer under ASTM D 4691-17 standard [49]. After observation using AAS, intensive properties were observed using a density test and probe test according to ASTM D-1298 [50] and ASTM D 5091-95 standards [51]. The use of standardized procedure is to ensure a better measurement for a valid research result.

Two different samples were prepared; pure paraffin (commercial grade 155/160, MSDS [52] and hybrid PCM consisting of 90% paraffin and 10% volcanic ash based on mass ratio. The addition of 10% volcanic ash was carried out with the aim to avoid decreased overall thermal capacity for the PCM as it was associated with a reduction in the capacity of paraffin as a PCM material. The test is carried out by using the High-Pressure High-Temperature apparatus (Fann HPHT) based on the ASTM D87-04. This test is carried out to determine important temperature changes in time units for the initial melting point

 $(T_{\rm melt})$ , fully melting point  $(T_{\rm Fmelt})$  and vapor point  $(T_{\rm vap})$  during the charging process and solidification point  $(T_{\rm solid})$  and fully solidification point  $(T_{\rm Fsolid})$  during the discharging process.

### RESULT AND DISCUSSION

### Sand Characterizations

Sand characterization starts from uniform sand size without going through a mechanical process [53]. The goal is to know the average particle size of the sand in general. Table 1 shows the size of the sand after finishing the sieve test.

Table 1. Screening particle size of the sand

Test	<b>Bulk Mass</b>	Percentage of
Sequence	(grams)	44 μm (%)
1	40.64	38.83
2	38.59	46.18
3	39.82	44.30
4	37.51	45.19
5	41.05	37.59
6	41.84	38.93
7	38.28	43.78
8	42.24	42.45
9	38.67	37.65
10	37.85	42.91

Based on the data in table 1, the average size of the sand 44  $\mu m$  is 41.72%. It is very beneficial because without going through the mechanical particle downsizing process, there is more than 40% of the 44  $\mu m$  size. The smaller size allows for better sand dispersion on PCM. In addition, the smaller size makes it easier for mechanical particle downsizing if needed for further process.

Uniform size facilitates the characterization process to determine chemical contain in the sand [54]. Table 2

represent the result for Atomic Absorption Spectrometer.

**Table 2.** Chemical contents from the sand

Elements	Percentage (%)
Fe	51.23
Fe203	23.24
SiO2	11
Others	14.53

The chemical content of sand is dominated by iron and iron oxide, both of which are known as excellent thermal conductivity elements. Excellent thermal conductivity will facilitate the heat transfer process on PCM and can increase the power rate of thermal energy storage. Intensive testing properties of the sand is shown in Table 3.

Table 3. Intensive properties of the sand

Elements	Value	Unit
Average	2.76	Gram/c
density	2.70	$m^3$
Conductiviy	291	μS/cm
pН	8.77	

Data table 3 supports the results of screening elements from table 2 where the dominance of metal elements causes a good sand conductivity value, the presence of iron oxide and silica oxide makes the pH value smaller, closer to neutral, and help to minimize the corrosivity rate in PCM.

## Charging and Discharging Performance

Tests were carried out on two samples: pure paraffin and hybrid PCM with a mass ratio of 90% paraffin and 10% volcanic ash. The test shows an important temperature indicator in each sample and help to understand the characteristics of the

temperature change per time. Figure 1 shows the pure paraffin charging test.

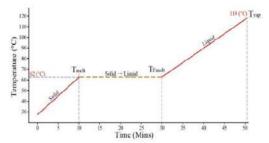


Figure 1. Charging for pure paraffin

Figure 1 the initial melting point ( $T_{melt}$ ) for the paraffin is reached within 10 mins at 62°C. The phase change (shown in brown dashed line) from initial melting point ( $T_{melt}$ ) to fully melt ( $T_{Fmelt}$ ) has done within 20 mins. As the heating process continued, the paraffin reachs the highest temperature point denoted as vapor point ( $T_{vap}$ ) at 119°C within 22 mins after the fully melting point ( $T_{Fmelt}$ ). The total charging time (from  $T_{ambient}$  to  $T_{vapor}$ ) is 52 mins, with temperature range from 27°C to 119°C.

To make a comparison, Figure 2 represents the characteristic of the paraffin during discharging process where the temperature drops from  $T_{vapor}$  to  $T_{ambient}$ .

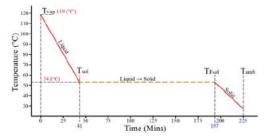


Figure 2. Discharging for pure paraffin


A significant difference is seen in the heat release process where it takes a longer time during discharging, the total time required for the paraffin to release the heat from T<sub>vapor</sub> to T<sub>ambient</sub> (119°C to 27°C) is 225 mins. In addition, phase changes also occur over a longer duration and it is related with the nature of the phase change material where it tends to release heat at longer period during phase change change. The most important information is the significant difference between the starting point of the melting process at charging process and the starting point of freezing during discharging. The difference between these two points is 8°C (T<sub>melt</sub> is 62°C and T<sub>sol</sub> is 54°C). The difference is known as supercooling phenomenon. A higher value of supercooling degree is a disadvantage because it makes the freezing process occur lower than the targeted temperature, leading to the possibility of decreasing the cycle of paraffin as thermal energy storage.

The addition of 10% sand to paraffin as a form of hybrid PCM material has a positive effect related to the increase in temperature absorption performance. Figure 3 shows the temperature and time function for hybrid PCM during charging process.

The positive effect from g volcanic ash into PCM can be seen from Figure 3 where the vapor point of the hybrid PCM is higher than the pure paraffin. The vapor point of hybrid PCM is 125 °C, higher 6 °C than pure paraffin. The increase in vapor point allows the hybrid PCM to work at relatively higher


Volume 6, Number 1, May 2021

temperatures so the stored energy during sensible heat may be higher.

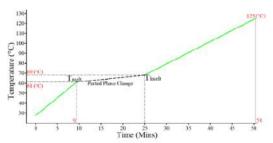

**Figure 3.** Charging for hybrid PCM (90% paraffin and 10% volcanic ash)

The next most important characteristic is that there is not fully phase change phenomenon as it observed from pure paraffin. It happens on hybrid PCM because it contains sensible material (volcanic ash) and led to a phenomenon called partial phase change or mushy region. The partial phase change promotes the increase in temperature can occur faster and allows an increase in the vapor point as seen in Figure 3. The phenomenon also gives the advantage that the charging process is faster where it takes 51 minutes to reach a higher vapor point.

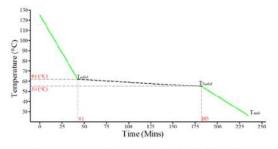

**Figure 4.** Discharging for hybrid PCM (90% paraffin and 10% volcanic ash)

For the final test of hybrid PCM, figure 4 shows the discharging process in the hybrid PCM. The total duration required for the

hybrid PCM to drop to ambient temperature from the vapor point is 235 mins, which is longer than pure paraffin which takes only 225 minutes. This condition is specifically caused by the influence of the supercooling degree. The melting point (during charging) and solidification (during discharging) in hybrid PCM is the same at 61 °C, which means that the supercooling degree is 0. It is an important finding because the addition of volcanic ash can prevent supercooling. g volcanic ash can provide a more even heat distribution effect on the PCM and able to prevent supercooling.

### CONCLUTIONS

The effort to improve the phase change material based on paraffin was done by g 10% volcanic ash with a particle size of 44  $\mu m$ . The addition of volcanic ash material to PCM provides the following advantages:

- a. Increase the vapor point from 119 °C to 125 °C, which means more energy can be absorbed by the hybrid PCM;
- b. Accelerates the charging process from 52 minutes to 51 minutes at higher temperatures (125 °C);
- Slows down the discharging process which means minimum heat losses.
- d. And the most important thing is in the hybrid PCM there is no supercooling phenomenon.

Taking this into account, the addition of volcanic ash sand with these properties and characteristics can provide good benefits for hybrid PCM as a thermal energy storage. This can be used as a basis information for further development of hybrid PCM thermal energy storage materials for low temperature applications or automotive thermal management systems to minimize heat loss from the engine. Further development can be focused on the model and design of a generator type heat exchanger for hybrid PCM in thermal management system applications or low temperature applications.

### REFERENCES

- [1] B. Ghorbani, K. B. Mahyari, M. Mehrpooya, and M. H. Hamedi, "Introducing a hybrid renewable benergy system for production of power and fresh water using parabolic trough solar collectors and LNG cold energy recovery," *Renew. Energy*, vol. 148, pp. 1227–1243, 2020.
- [2] R. Ling-zhi, Z. Xin-gang, Z. Yu-zhuo, and L. Yan-bin, "The Economic Performance of Concentrated Solar Power industry in China," *J. Clean. Prod.*, vol. 205, no. 20 Desember 2018, 2018.
- [3] A. Peinado Gonzalo, A. Pliego Marugán, and F. P. García Márquez, "A review of the application performances of concentrated solar power systems," Appl. Energy, vol. 255, no. March, p. 113893, 2019.
- [4] A. M. Junior and M. B. H. Mantelli, "Thermal performance of a novel flat thermosyphon for avionics thermal management," Energy Convers. Manag.,

- Dwi Chandra Adhitya, Dwi Rahmalina, Ismail, Muhammad Nurtanto, Hamid Abdillah s a basis information for further vol. 202, no. November, p. 112219, of hybrid PCM thermal energy 2019.
  - [5] A. Naidoo, "The socio-economic impacts of solar water heaters compared across two communities: A case study of Cato Manor," Renew. Sustain. Energy Rev., vol. 119, no. November 2019, p. 109525, 2020.
  - [6] A Voirand, S. Lips, and V. Sartre, "Heat transfer and flow visualizations in a flat confined two-phase thermosyphon," *Int. J. Heat Mass Transf.*, vol. 148, no. xxxx, p. 119056, 2020.
  - [7] T. A. Yassen, N. D. Mokhlif, and M. A. Eleiwi, "Performance investigation of an integrated solar water heater with corrugated absorber surface for domestic use," *Renew. Energy*, vol. 138, no. August 2019, pp. 852–860, 2019.
  - [8] H. J. Mosleh, S. J. Mamouri, M. B. Shafii, and A. H. Sima, "A new desalination system using a combination of heat pipe, evacuated tube and parabolic through collector," *ENERGY Convers. Manag.*, vol. 99, no. 15 July 2015, pp. 141–150, 2015.
  - [9] A. Kasaeian, F. Rajaee, and W. Yan, "Osmotic Desalination by Solar Energy: A Critical Review," Renew. Energy, vol. 134, no. April 2019, pp. 1473–1490, 2018.
  - [10] S. Raja Narayanan and S. Vijay, "Desalination of water using parabolic trough collector," *Mater. Today Proc.*, vol. 21, no. Part 1, pp. 375–379, 2020.

- [11] L. Gao, G. Tian, A. Sorniotti, A. E. Karci, and R. Di Palo, "Review of thermal management of catalytic converters to decrease engine emissions during cold start and warm up," *Appl. Therm. Eng.*, vol. 147, no. 25 January 2019, pp. 177–187, 2019.
- [12] S. Wiriyasart, C. Hommalee, S. Sirikasemsuk, R. Prurapark, and P. Naphon, "Thermal management system with nanofluids for electric vehicle battery cooling modules," *Case Stud. Therm. Eng.*, vol. 18, no. December 2019, p. 100583, 2020.
- [13] P. Xu, C. Ji, S. Wang, X. Bai, and X. Cong, "ScienceDirect Realizing low emissions on a hydrogen-fueled spark ignition engine at the cold start period under rich combustion through ignition timing control," *Int. J. Hydrogen Energy*, vol. 44, no. 16, pp. 8650–8658, 2019.
- [14] H. Lund *et al.*, "Energy Storage and Smart Energy Systems," *Int. J. Sustain. Energy Plan. Manag.*, vol. 11, pp. 3–14, 2016.
- [15] A. D'Entremont, C. Corgnale, M. Sulic,
  B. Hardy, R. Zidan, and T. Motyka,
  "Modeling of a thermal energy storage
  system based on coupled metal
  hydrides (magnesium iron sodium
  alanate) for concentrating solar power
  plants," Int. J. Hydrogen Energy, vol. 42,
  no. 35, pp. 22518–22529, 2017.
- [16] A. D'Entremont, C. Corgnale, B. Hardy, and R. Zidan, "Simulation of high

- temperature thermal energy storage system based on coupled metal hydrides for solar driven steam power plants," *Int. J. Hydrogen Energy*, vol. 43, no. 2, pp. 817–830, 2018.
- [17] D. A. Sheppard and C. E. Buckley, "The notential of metal hydrides paired with compressed hydrogen as thermal energy storage for concentrating solar power plants," Int J. Hydrogen Energy, vol. 44, no. 18, pp. 9143-9163, 2019.
- [18] F. Jamadi, M. Arabpour, and M. Abdolzadeh, "Performance comparison of parabolic and flat plate solar collectors utilizing in the heating system of a room-an experimental investigation," Int. J. Renew. Energy Res., vol. 7, no. 4, pp. 1836–1849, 2017.
- [19] S. S. Mostafavi Tehrani, Y. Shoraka, K. Nithyanandam, and R. A. Taylor, "Shell-and-tube or packed bed thermal energy storage systems integrated with a concentrated solar power: A techno-economic comparison of sensible and latent heat systems," Appl. Energy, vol. 238, no. November 2017, pp. 887–910, 2019.
- [20] S. Turrini, M. Bettonte, M. Eccher, M. Grigiante, and R. S. Brusa, "An innovative small-scale prototype plant integrating a solar dish concentrator with a molten salt storage system," Renew. Energy, vol. 123, no. August 2018, pp. 150–161, 2018.
- [21] S. Narayanan *et al.*, "Thermal battery for portable climate control," *Appl.*

*Energy*, vol. 149, no. 1 July 2015, pp. 104-116, 2015.

- [22] Manickam et al., "Future perspectives of thermal energy storage with metal hydrides," Int. J. Hydrogen Energy, vol. 44, no. 15, pp. 7738-7745, 2019.
- [23] IRENA, Innovation Outlook: Thermal Energy Storage. Abu Dhabi: International Renewable Energy Agency, 2020.
- [24] Q. Wang, D. Zhou, Y. Chen, P. Eames, and Z. Wu, "Characterization and effects of thermal cycling on the properties of paraffin/expanded graphite composites," Renew. Energy, vol. 147, no. March 2020, pp. 1131-1138, 2020.
- [25] H. El-Dessouky and F. Al-Juwayhel, "Effectiveness of a thermal energy storage system using phase-change materials," Energy Convers. Manag., vol. 38, no. 6, pp. 601-617, 1997.
- [26] B. Kanimozhi, K. Harish, B. S. Tarun, P. S. Sainath Reddy, and P. S. Sujeeth, "Charging and Discharging Processes of Thermal Energy Storage System Using Phase change materials," IOP Conf. Ser. Mater. Sci. Eng., vol. 197, no. 1, pp. 0-7, 2017.
- [27] R. Nivaskarthick, "Analysis of Thermal Energy Storage system using Paraffin Wax as Phase Change Material," Conf. Int. Conf. Innov. Eng. Technol., vol. 1, no. 2, pp. 38-47, 2016.
- [28] I. Sarbu and C. Sebarchievici, "A

- Dwi Chandra Adhitya, Dwi Rahmalina, Ismail. Muhammad Nurtanto, Hamid Abdillah comprehensive review of thermal energy storage," Sustain., vol. 10, no. 1, pp. 1-32, 2018.
  - G. Hailu, P. Hayes, and M. Masteller, "Seasonal solar thermal energy sandbed storage in a region with extended freezing periods: Part I experimental investigation," Energies, vol. 10, no. 11, pp. 1-12, 2017.
  - Y. Cai, Q. Wei, F. Huang, S. Lin, F. Chen, and W. Gao, "Thermal stability, latent heat and flame retardant properties of the thermal energy storage phase change materials based on paraffin / high density polyethylene composites," Renew. Energy, vol. 34, no. 10, pp. 2117-2123, 2009.
  - [31] S. Wu, G. Fang, and X. Liu, "Dynamic discharging characteristics simulation on solar heat storage system with spherical capsules using paraffin as heat storage material," Renew. Energy, vol. 36, no. 4, pp. 1190-1195, 2011.
  - [32] A. Reyes, L. Henriquez-Vargas, J. Vásquez, N. Pailahueque, and G. Aguilar, "Analysis of a laboratory scale thermal energy accumulator using two-phases heterogeneous paraffin wax-water mixtures," Renew. Energy, vol. 145, no. January 2020, pp. 41-51, 2020.
  - B. Prabhu and A. ValanArasu, "Stability analysis of TiO2-Ag nanocomposite particles dispersed paraffin wax as energy storage material for solar thermal systems," Renew. Energy, vol.

- Dwi Chandra Adhitya, Dwi Rahmalina, Ismail, Muhammad Nurtanto, Hamid Abdillah 152, no. June 2020, pp. 358–367, 2020. for a solar application: Simulation
- [34] H. Nikpourian, A. R. Bahramian, and M. Abdollahi, "On the thermal performance of a novel PCM nanocapsule: The effect of core/shell," Renew. Energy, vol. 151, no. May 2020, pp. 322–331, 2020.
- [35] X. Zuo, J. Li, X. Zhao, H. Yang, and D. Chen, "Emerging paraf fi n / carbon-coated nanoscroll composite phase change material for thermal energy storage," *Renew. Energy*, vol. 152, no. June 2020, pp. 579–589, 2020.
- [36] N. Ahmed, K. E. Elfeky, L. Lu, and Q. W. Wang, "Thermal performance analysis of thermocline combined sensible-latent heat storage system using cascaded-layered PCM designs for medium temperature applications," Renew. Energy, vol. 152, no. June 2020, pp. 684–697, 2020.
- [37] A. Jawad, A. M. J. Mahdy, A. H. Khuder, and M. T. Chaichan, "Improve the performance of a solar air heater by adding aluminum chip, paraffin wax, and nano-SiC," Case Stud. Therm. Eng., vol. 19, no. March 2020, p. 100622, 2020.
- [38] R. Elbahjaoui and H. El Qarnia, "Performance evaluation of a solar thermal energy storage system using nanoparticle-enhanced phase change material," *Int. J. Hydrogen Energy*, vol. 44, no. 3, pp. 2013–2028, 2019.
- [39] N. Mahfoudi, A. Moummi, and M. El Ganaoui, "Sand as a heat storage media

- for a solar application: Simulation results," *Appl. Mech. Mater.*, vol. 621, no. August 2014, pp. 214–220, 2014.
- [40] B. Sivapalan, M. Neelesh Chandran, S. Manikandan, M. K. Saranprabhu, S. Pavithra, and K. S. Rajan, "Paraffin wax-water nanoemulsion: A superior thermal energy storage medium providing higher rate of thermal energy storage per unit heat exchanger volume than water and paraffin wax," *Energy Convers. Manag.*, vol. 162, no. February, pp. 109–117, 2018.
- [41] P. Zhang, Z. N. Meng, H. Zhu, Y. L. Wang, and S. P. Peng, "Melting heat transfer characteristics of a composite phase change material fabricated by paraffin and metal foam," *Appl. Energy*, vol. 185, no. 1 January 2017, pp. 1971–1983, 2017.
- [42] A Frazzica, M. Manzan, A. Sapienza, A. Freni, G. Toniato, and G. Restuccia, "Experimental testing of a hybrid sensible-latent heat storage system for domestic hot water applications," Appl. Energy, vol. 183, no. 1 December 2016, pp. 1157–1167, 2016.
- [43] A Palacios, M. Elena Navarro, C. Barreneche, and Y. Ding, "Hybrid 3 in 1 thermal energy storage system 45 Outlook for a novel storage strategy," Appl. Energy, vol. 274, no. April, p. 115024, 2020.
- [44] S. Drissi, T. Ling, and K. Hung, "Thermochimica Acta Thermal

Dwi Chandra Adhitya, Dwi Rahmalina, Ismail, Muhammad Nurtanto, Hamid Abdillah

- efficiency and durability performances of paraffinic phase change materials with enhanced thermal conductivity A review," *Thermochim. Acta*, vol. 673, no. August 2018, pp. 198–210, 2019.
- [45] M. Diago, A. C. Iniesta, A. Soum-Glaude, and N. Calvet "Characterization of desert sand to be used as a high-temperature thermal energy storage medium in particle solar receiver technology," *Appl. Energy*, vol. 216, no. October 2017, pp. 402–413, 2018.
- [46] P. Dumka, A. Sharma, Y. Kushwah, A. S. Raghav, and D. R. Mishra, "Performance evaluation of single slope solar still augmented with sand-filled cotton bags," *J. Energy Storage*, vol. 25, no. August, p. 100888, 2019.
- [47] G. Hailu, P. Hayes, and M. Masteller, "Long-term monitoring of sensible thermal storage in an extremely cold region," *Energies*, vol. 12, no. 9, pp. 1–19, 2019.
- [48] R. Gulfam, P. Zhang, and Z. Meng, "Advanced thermal systems driven by paraffin-based phase change materials A review," *Appl. Energy*, vol. 238, no. June 2018, pp. 582–611, 2019.
- [49] A. S. for T. and Materials, Standard Practice for Measuring Elements in Water by Flame Atomic Absorption Spectrophotometry, Vol. Sec.,. ASTM, 2010.

- [50] A. S. for T. and Materials, Standard Test Methods for Density, Relative Density (Specific Gravity), or API Gravity of Crude Petroleum and Liquid Petroleum Products by Hydrometer Method. ASTM, 1999.
- [51] American Society for Testing and Materials, Measuring and Recording Water Quality Parameters for Monitoring Purposes. ASTM, 2014.
- [52] N. Ukrainczyk, S. Kurajica, and J. Šipušić, "Thermophysical comparison of five commercial paraffin waxes as latent heat storage materials," *Chem. Biochem. Eng. Q.*, vol. 24, no. 2, pp. 129–137, 2010.
- [53] Lutiyatmi, T. Daryanto, and H. Abdillah, "PENERAPAN FACE SAND PADA PASIR CETAK UNTUK MENGURANGI REJECT PRODUK DI PT. MITRA KARYA UTAMA (IMPLEMENTATION OF FACE SAND ON SAND MOLD TO REDUCE PRODUCT REJECT IN PT. MITRA KARYA UTAMA)," J. Berdaya Mandiri, vol. 3, no. 1, pp. 518–528, 2021.
- [54] S. I. Khasanah, N. R. Sesunan, and H. Abdillah, "Study of the reclamation of waste co2 moulding sand in foundry industry," *Int. J. Emerg. Trends Eng. Res.*, vol. 8, no. 9, pp. 5454–5459, 2020.

# Thermal Enhancement for Paraffinic Thermal Energy Storage by Adding Volcanic Ash

**ORIGINALITY REPORT** 

19% SIMILARITY INDEX

12%
INTERNET SOURCES

18%
PUBLICATIONS

10%

STUDENT PAPERS

**PRIMARY SOURCES** 

Husni Ibadi, Ahmad Sangidzun, Danar Susilo Wijayanto, Herman Saputro, Soenarto, M Bruri Triyono. "Effect of Adding of Pitch on the Darrieus Blade Against the Cut In Speed of the Savonius Type S - Darrieus Type H Hybrid Turbine", Journal of Physics: Conference Series, 2021

3%

Publication

www.hindawi.com

1 %

Submitted to IIT Delhi
Student Paper

1 %

Liqiang Deng, Yong Li, Peiken Xu, Zhaoshu Chen, Wenjie Zhou, Bo Li. "Fabrication and thermal performance of a novel roll-bond flat thermosyphon", Applied Thermal Engineering, 2020

1 %

Publication

5

Moustafa M. Aboelmaaref, Mohamed E. Zayed, Jun Zhao, Wenjia Li, Ahmed A.

1 %

Askalany, M. Salem Ahmed, Ehab S. Ali.
"Hybrid solar desalination systems driven by parabolic trough and parabolic dish CSP technologies: Technology categorization, thermodynamic performance and economical assessment", Energy Conversion and Management, 2020

Publication

Ahmad K. Sleiti. "Heat transfer measurements of Polyalpha-Olefin- boron nitride nanofluids for thermal management and lubrication applications", Case Studies in Thermal Engineering, 2020

1 %

Publication

Dong-Shuo Ma, Z.Y. Sun. "Progress on the studies about NOx emission in PFI-H2ICE", International Journal of Hydrogen Energy, 2019

1 %

Publication

Mohamed Krarouch, Florian Ruesch, Hassan Hamdi, Abdelkader Outzourhit, Michel Haller. "Dynamic simulation and economic analysis of a combined solar thermal and pellet heating system for domestic hot water production in a traditional Hammam", Applied Thermal Engineering, 2020

1%

Publication

B. Eanest Jebasingh, A. Valan Arasu. "A **1** % 10 detailed review on heat transfer rate, supercooling, thermal stability and reliability of nanoparticle dispersed organic phase change material for low-temperature applications", Materials Today Energy, 2020 Publication Submitted to Free University of Bolzano <1% Student Paper M.M. El-Khouly, M.A. El Bouz, G.I. Sultan. 12 "Experimental and computational study of using nanofluid for thermal management of electronic chips", Journal of Energy Storage, 2021 **Publication** d-nb.info <1% Internet Source backend.orbit.dtu.dk Internet Source Submitted to University of Malaya Student Paper Hamdy Hassan, M. Salem Ahmed, Mohamed 16 Fathy, Mohamed S. Yousef. "Impact of salty

water medium and condenser on the

performance of single acting solar still incorporated with parabolic trough collector", Desalination, 2020

Publication

Nurul Akmal Che Lah. "Late transition metal <1% 17 nanocomplexes: Applications for renewable energy conversion and storage", Renewable and Sustainable Energy Reviews, 2021 **Publication** Hediyeh Nikpourian, Ahmad Reza Bahramian, <1% 18 Mahdi Abdollahi. "On the thermal performance of a novel PCM nanocapsule: The effect of core/shell", Renewable Energy, 2020 Publication Submitted to University of Nottingham <1% 19 Student Paper res.mdpi.com 20 Internet Source sersc.org 21 Internet Source <1% Mohammadreza Sedighi, Ricardo Vasquez 22 Padilla, Pedram Alamdari, Maree Lake, Andrew Rose, Iman Izadgoshasb, Robert A. Taylor. "A novel high-temperature (>700 °C), volumetric receiver with a packed bed of

23	Andre Bolt, Ibrahim Dincer, Martin Agelin-Chaab. "A new integrated system with thermal energy storage for five useful outputs: A case study", Sustainable Energy Technologies and Assessments, 2021 Publication	<1%
24	Submitted to University of Southampton Student Paper	<1%
25	ZILONG DENG, XUAN ZHANG, YAN ZHANG, SHUSEN JIANG, CHENG YU. "THERMAL ENERGY CHARGING IMPROVEMENT OF A LATENT THERMAL ENERGY STORAGE SYSTEM VIA FRACTAL-BRANCHED FINS", Fractals, 2021 Publication	<1%
26	G. Srinivasan, P. Muthukumar. "A review on solar greenhouse dryer: Design, thermal modelling, energy, economic and environmental aspects", Solar Energy, 2021  Publication	<1%
27	Wu, S "Dynamic discharging characteristics simulation on solar heat storage system with spherical capsules using paraffin as heat storage material", Renewable Energy, 201104	<1%

combined cooling and power cycle driven by solar energy", Thermal Science and Engineering Progress, 2020

Publication

34	Seyed Mostapha Musavi, Farahnaz Barahuie, Mohsen Irani, Ali Safamanesh, Abdurahman Malekpour. "Enhanced properties of phase change material -SiO2-graphene nanocomposite for developing structural–functional integrated cement for solar energy absorption and storage", Renewable Energy, 2021 Publication	<1%
35	Submitted to Universitas Sultan Ageng Tirtayasa Student Paper	<1%
36	journals.vgtu.lt Internet Source	<1%
37	www.mbarnesdds.com Internet Source	<1%
38	A. Reyes, L. Henríquez-Vargas, J. Rivera, F. Sepúlveda. "Theoretical and experimental study of aluminum foils and paraffin wax mixtures as thermal energy storage material", Renewable Energy, 2017 Publication	<1%

39	Najoua Mekaddem, Samia Ben Ali, Ahmed Hannachi, Atef Mazioud, Magali Foi. "Latent energy storage study in simple and honeycomb structures filled with a phase change material", 2016 7th International Renewable Energy Congress (IREC), 2016 Publication	<1%
40	art.torvergata.it Internet Source	<1%
41	figshare.com Internet Source	<1%
42	www.sdewes.org Internet Source	<1%
43	Ammar Alkhalidi, Hamzah Al Khatba, Mohamad K. Khawaja. "Utilization of Buildings' Foundations for a Seasonal Thermal Energy Storage Medium to Meet Space and Water Heat Demands", International Journal of Photoenergy, 2021 Publication	<1%
44	Bhargav H. Upadhyay, Amitkumar J. Patel, P. V. Ramana. "A detailed review on solar parabolic trough collector", International Journal of Ambient Energy, 2019	<1%
45	Anabel Palacios, M. Elena Navarro, Camila Barreneche, Yulong Ding. "Hybrid 3 in 1	<1%

thermal energy storage system – Outlook for a novel storage strategy", Applied Energy, 2020

Publication

C. Suresh, R.P. Saini. "Experimental study on combined sensible-latent heat storage system for different volume fractions of PCM", Solar Energy, 2020

<1%

Publication

Tianhao Xu, Saman Nimali Gunasekara, Justin Ningwei Chiu, Björn Palm, Samer Sawalha. "Thermal behavior of a sodium acetate trihydrate-based PCM: T-history and full-scale tests", Applied Energy, 2020

<1%

- Publication
- Valeria Palomba, Vincenza Brancato, Giulia Palomba, Silvia Borsacchi, Claudia Forte, Angelo Freni, Andrea Frazzica. "Latent Thermal Storage for Solar Cooling Applications: Materials Characterization and Numerical Optimization of Finned Storage Configurations", Heat Transfer Engineering, 2018

<1%

Publication

Exclude quotes Off
Exclude bibliography On